

Chemical Science

Accepted Manuscript

This article can be cited before page numbers have been issued, to do this please use: L. Lu and H. Wang, *Chem. Sci.*, 2026, DOI: 10.1039/D5SC07607B.



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

PERSPECTIVE

Liquid–Liquid Phase Separation of Peptides: A Molecular Foundation for Next-Generation Biomaterials

Received 00th January 20xx,
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

Liheng Lu^a and Huaimin Wang^{*a}

Liquid–liquid phase separation (LLPS) is a key mechanism for organizing membraneless cellular compartments, influencing processes like stress response, signaling, and gene regulation. While intrinsically disordered proteins (IDPs) and their regions (IDRs) drive LLPS through weak, multivalent interactions, the complexity of full-length proteins limits systematic design and understanding of phase separation. Peptides, as simpler modular units, offer precise control over sequence composition and provide a scalable platform for studying LLPS. Recent advancements demonstrate that peptide condensates reveal fundamental phase separation rules and enable applications such as artificial cells and drug delivery systems. This Perspective highlights recent progress in peptide LLPS, focusing on sequence design, structural characterization, and emerging applications, and discusses challenges and future directions for broader applications.

1 Introduction

Liquid–liquid phase separation (LLPS) has emerged as a central principle for organizing biomolecules in cells,^{1–4} enabling the formation of dynamic, membraneless condensates such as stress granules, nucleoli, and signaling hubs.^{5–7} These condensates provide confined environments that concentrate specific molecules, regulate biochemical reactions, and allow rapid responses to environmental cues.^{8–11} The conceptual origins of LLPS trace back to early solution thermodynamics and phase diagram analyses by Van't Hoff and Gibbs, later expanded by polymer theories such as the Flory–Huggins model.^{9, 12} Since the discovery that *C. elegans* P granules behave as liquid droplets rather than static particles,⁵ followed by in vitro reconstitution of protein–RNA condensates, LLPS has been recognized as a general organizing mechanism across diverse cellular contexts.^{13–20} Its dysregulation is increasingly linked to pathologies including neurodegeneration, cancer, and immune dysfunction, underscoring both its physiological importance and therapeutic relevance.^{21–23}

Mechanistic studies of LLPS have traditionally focused on intrinsically disordered proteins (IDPs) and intrinsically disordered regions (IDRs), which contain multivalent motifs that mediate weak but cooperative interactions such as electrostatic interaction, π – π stacking, and cation– π interaction.^{8, 24–26} While these systems have revealed much about the molecular grammar of phase separation, the complexity of full-length proteins poses persistent challenges. Their long sequences, modular domains, and extensive post-translational modifications make it difficult to isolate the contribution of specific residues or to systematically test design rules. Moreover, high valency is often required for proteins to phase-separate at physiological

concentrations, which complicates experimental tractability and limits high-throughput exploration.

Peptides are now emerging as simplified and programmable building blocks for LLPS, offering a complementary approach to protein-based studies. As the smallest modular units, peptides retain essential interaction motifs while providing precise control over sequence composition, length, and valency.^{27–29} Their chemical accessibility enables rapid synthesis, systematic library construction, and facile incorporation of functional groups. In this way, peptides bridge a critical gap: they are biologically relevant enough to mimic features of protein condensates, yet minimal enough to enable mechanistic dissection and rational design.

This Perspective focuses specifically on peptide materials driven by LLPS. We highlight how sequence determinants and intermolecular forces govern condensate formation, and how external stimuli (e.g., pH, temperature, redox state, and enzymatic activity) regulate condensate dynamics. We then discuss how these principles translate into emerging applications, including programmable delivery systems, microreactors, and artificial organelles. Finally, we outline the challenges that must be addressed, such as predictive sequence design, stability in complex environments, and integration of multifunctional modules, to fully realize peptide LLPS as a versatile platform for chemistry, bioengineering, and medicine. (Fig. 1)

2 Mechanistic Basis and Design of Peptide Condensates through LLPS

2.1 Sequence Composition and the “Sticker–Spacer” Model

Peptide LLPS arises from multivalent interactions between “sticker” residues (typically aromatic or charged amino acids) connected by flexible “spacers” that regulate chain mobility.^{24, 30, 31} Compared with long proteins, short peptides have lower valency, and thus require either stronger per-residue interactions or favorable thermodynamic compensation to phase-separate at low concentrations.^{32–35}

^a Department of Chemistry, School of Science, Westlake University, No. 600 Dunyu Road, Hangzhou 310024, Zhejiang Province, China.



Incorporating residues with the capability of providing strong and directional interactions is thus essential for effective LLPS in minimal

peptide systems.

[View Article Online](#)
DOI: 10.1039/D5SC07607B

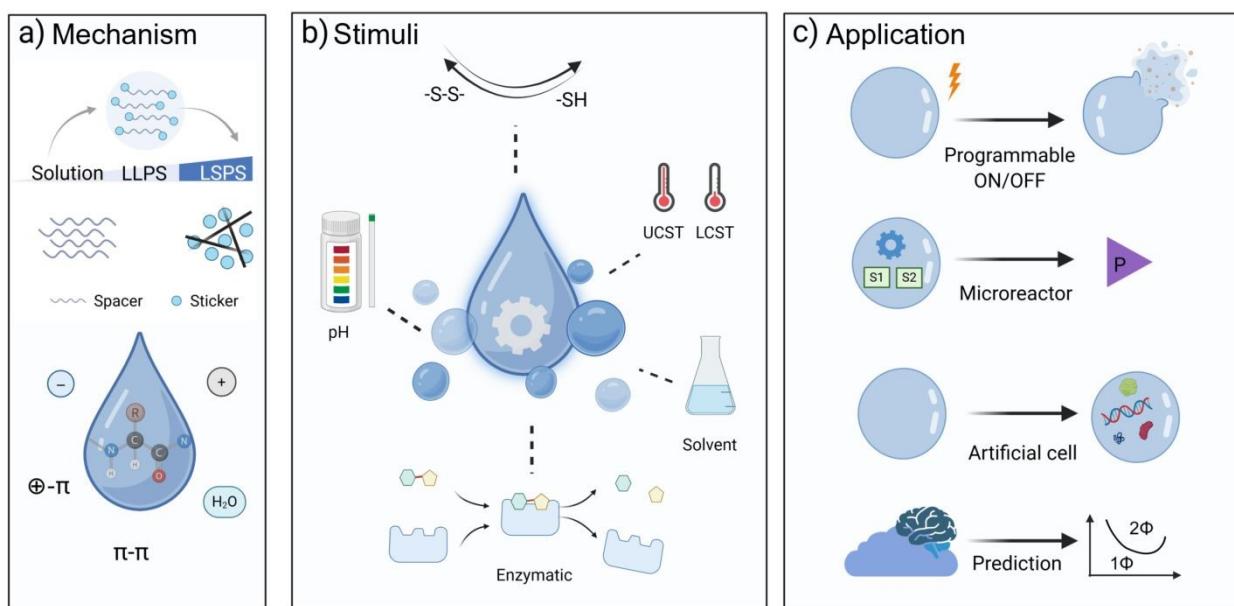


Fig. 1 Programmable peptide LLPS from mechanisms to functions. a) Mechanism: Sticker–spacer framework, where aromatic, charged, or H-bonding stickers drive reversible interactions, and spacers maintain solvation and mobility. b) Stimuli: Redox state, temperature (UCST/LCST), pH, solvent, and enzymatic cues modulate condensate assembly. c) Applications: Programmable ON/OFF control, microreactors, artificial-cell systems, and data-driven design. Created in BioRender with confirmation: CC28TBO2BN.

Aromatic amino acids such as phenylalanine (F), tyrosine (Y), and especially tryptophan (W) serve as potent stickers due to their extended π -electron systems, hydrophobicity,^{36–38} and in the case of W, additional hydrogen bonding potential from its indole NH group. Artificial enrichment of these residues can significantly enhance LLPS propensity (Fig. 2a). For example, Zhou *et al.* designed WXXW tetrapeptides (X = amino acid residue) that formed droplets at high concentration, with increased sticker density (e.g., WXWW) reducing the critical concentration for phase separation.³⁹ These studies show that even in minimal sequences, tuning sticker number and arrangement provides programmable control over condensate behavior.

2.2 Forces for Driving LLPS

Beyond sequence composition, condensate stability is governed by the balance and reversibility of underlying noncovalent interactions (Fig. 2b).^{40,41} Electrostatics interactions are often dominant in charged peptide systems and peptide–nucleic acid coacervates,⁴² whereas hydrophobic interactions can drive LLPS in neutral peptide by promoting water exclusion and lowering the free energy of phase separation.³⁶ Aromatic–aromatic interactions, π – π stacking and cation– π interactions (e.g., between arginine and aromatics residues) further enhance cohesion, and hydrogen bonding or dipole–dipole interactions from polar residues can modulate internal organization and mobility within condensates.⁴³ Castelletto *et al.* demonstrated that combining aromatic groups with arginine strongly promotes LLPS in minimal peptides, tuning the formation of droplet and controlling their dynamics.³³ Such findings reinforce that condensates are stabilized

not by a single force but by a cooperative network of weak interactions.

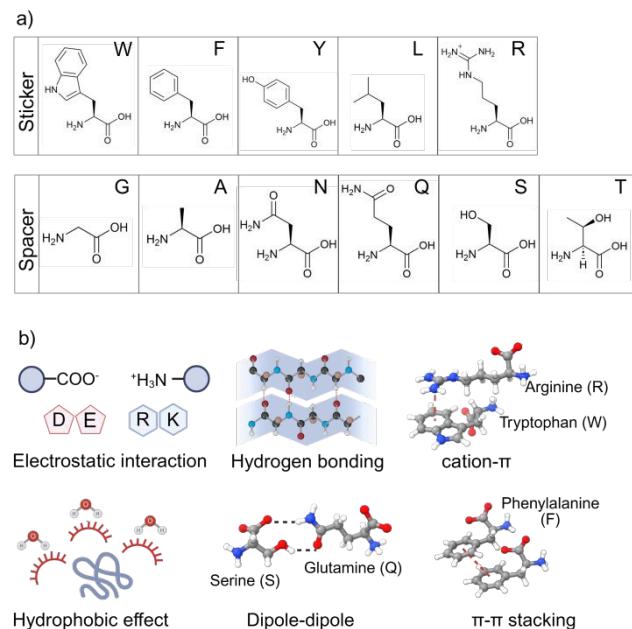


Fig. 2 Sequence grammar and multivalent interactions in peptide LLPS. a) Representative amino acid residues functioning as stickers and spacers in short peptide sequences; b) Schematic illustration of major multivalent interactions driving LLPS, including electrostatic attraction, hydrogen bonding, cation– π contacts, hydrophobic association, dipole–dipole interactions, and π – π stacking. (Created in BioRender with confirmation: DW28TBQZNL)

Together, the sticker-spacer framework and the types of driving forces provide a rational design basis for peptide LLPS. By selectively varying residue type, valency, and patterning, one can shift critical concentrations, modulate material states, or introduce responsiveness. Beyond the sticker-spacer framework, peptide LLPS can also emerge from alternative strategies such as solvation–desolvation dynamics, sequence-encoded polarity gradients, or environmentally triggered changes in charge or hydrophobicity, which collectively broaden the molecular strategies available for designing minimal condensate-forming peptides. These principles not only clarify the minimal requirements for condensation but also offer a blueprint for engineering peptide-based assemblies with tailored functions.

3 Physicochemical Properties of Peptide-Based Condensates through LLPS

Minimal peptides challenge the traditional view of biomolecular condensates as homogeneous liquid droplets. Instead, their phase-separated assemblies reveal surprising levels of structural complexity, ranging from multiphase organization to solvent-driven transitions and diverse dynamic states.^{14, 44} These properties are not incidental but encode fundamental rules for how short peptide sequences interact with each other and with their environment. We argue that uncovering these rules is central to transforming LLPS of peptide from a descriptive phenomenon into a rationally engineerable platform.

3.1 Internal Architecture and Multiphase Organization

The microenvironment of peptide condensates formed through LLPS has often been overlooked, with droplets typically assumed to be homogeneous in organization. However, recent studies have revealed that condensates can display internal heterogeneity and evolving structural features, motivating closer examination of their microstructural dynamics. For example, Zhou and colleagues⁴⁵ reported that a library of programmable tetrapeptides can form core–shell condensates even though they are single-component systems (Fig. 3). In their work, they systematically varied sticker density by inserting glycine spacers into di-tryptophan motifs to tune the balance between π – π stacking, hydrophobic contacts, and peptide–water interactions. As shown in Fig. 3a, increasing the number of glycine spacers (e.g., WW \rightarrow WGGW) progressively reduces aromatic interaction strength and enhances hydration, providing a design rationale for modulating condensate architecture. Cryo-focused ion beam scanning electron microscopy (cryo-FIB–SEM, Fig. 3b) images revealed that the WW peptide forms droplets with a dense, solid-like tryptophan-rich core enveloped by a more fluid shell, whereas glycine-containing analogues yield fully homogeneous droplets. This structural interpretation is supported by fluorescence-lifetime imaging (FLIM), FRAP fusion dynamics, and Raman/FTIR measurements, which collectively show that weakening peptide–peptide interactions and strengthening peptide–water hydrogen bonding drives the transition from core–shell organization to uniformly liquid condensates. These findings highlight how small sequence modifications in minimal peptides can generate diverse internal architectures through controlled modulation of interaction strengths and hydration. Besides, Netzer *et al.* demonstrated that systematic tuning of aromatic residue type and arrangement could regulate the

internal organization of peptide condensates, enabling transitions from homogeneous droplets to layered structures.¹⁹ Their work revealed that cation– π interactions act synergistically with hydrophobic forces to drive spatial compartmentalization. Recently, Ye *et al.*⁴⁷ showed that sufficient micropolarity contrast between layers favors the emergence of multilayered architecture, with the shell being more polar than the core, and that inversion of micropolarity corresponds to restructuring of layers.

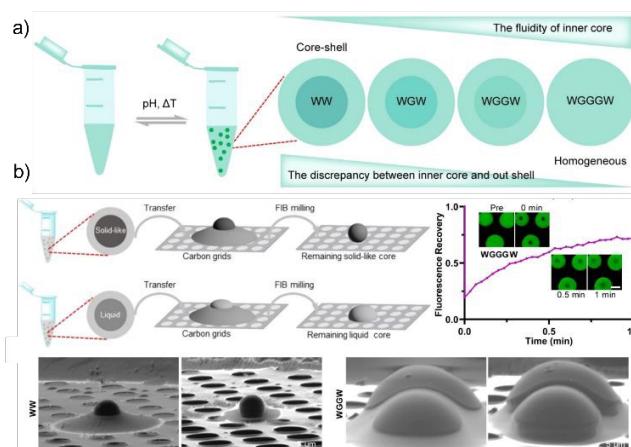


Fig. 3 Internal architectures of peptide condensates. a) Increasing the ratio of tryptophan residues tunes condensate architectures from homogeneous droplets to core–shell structures with reduced inner fluidity. b) Schematic illustration of the changes of the condensates under gallium ion beam sputtering, and cryo-FIB–SEM images of the droplets formed by WW and WGGW.

These findings indicated that, beyond overall sticker density or spacing, variations in local polarity and interaction strength within the condensate can bias droplets toward internally layered rather than homogeneous organization. In peptide-based systems, even modest gradients in hydrophobicity or polarity may be sufficient to promote such internal segregation. This implies that multiphase organization is not necessarily rare, but can emerge when sequences exceed certain thresholds of heterogeneity. Designing peptides with controlled polarity gradients or differential interaction motifs may therefore provide a route to encode spatially distinct microenvironments within condensates, enabling compartmentalization of functions such as catalysis versus storage.

3.2 Hydration and Desolvation Processes

Hydration plays a central role in phase separation, as the balance between peptide–water affinity and peptide–peptide interactions determines whether systems undergo condensation or remain dispersed.^{48–50} Wang *et al.* demonstrated that changes in water structure accompany condensate formation, and that progressive dewetting of hydration shells is closely associated with liquid to solid transitions.⁴⁵ In this view, strong peptide–peptide networks coupled with weakened hydration promote the formation of solid-like cores, whereas sustained hydration supports more homogeneous, liquid-like droplets (Fig. 4a).



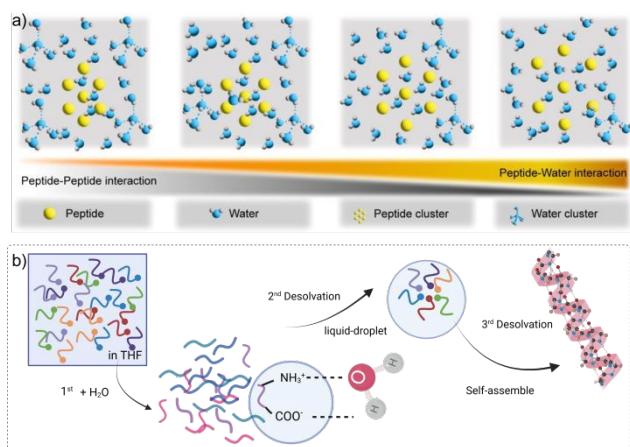


Fig. 4 Multistep desolvation and peptide–water interaction in peptide LLPS. a) Schematic illustration of the shift in interaction balance from peptide–peptide clustering to peptide–water and water–water association, exemplified by the transition from WW to WGGGW systems. b) Schematic illustration of multistep desolvation process that drives peptide LLPS, illustrating the progression from initial peptide solution to liquid-droplet formation and subsequent self-assembly. (Created in BioRender with confirmation: ZJ28TBUH11)

More specifically, Yuan *et al.* proposed a multistep desolvation mechanism in peptide assemblies through LLPS.⁵¹ According to their model, condensation proceeds via three stages (Fig. 4b): (1) partial desolvation and solvent exchange, (2) selective desolvation of hydrophobic moieties triggering phase separation into peptide-rich droplets, and (3) further desolvation inside droplets that leads to nucleation and internal ordering. They demonstrated this with model peptides (e.g. TPPGFF in mixed solvents), tracking structural intermediates *via* cryo-TEM, mass spectrometry, NMR, and MD simulation. This model connects early hydration-governed organization to later droplet-to-fiber or gel transitions, highlighting hydration–desolvation balance as a key axis for tuning condensate properties through solvent engineering.

Solvent is often treated as a passive background in design strategies, but in peptide LLPS it can act as an active co-determinant of behavior. Because minimal peptide sequences are highly sensitive to solvent effects, tuning parameters such as ionic strength, osmolytes, cosolvents, or hydration dynamics can markedly alter phase behavior. In practice, modulating desolvation kinetics (e.g., by adjusting solvent exchange rates or introducing weak cosolutes) offers a route to control droplet stability, morphology, and maturation pathways that is orthogonal to sequence-based design.^{52,53} In designing peptide-based condensates, stability of the liquid droplet phase requires a balance: interactions must be strong enough to drive LLPS but not so strong as to promote irreversible aggregation or precipitation. This balance can be tuned by modulating sticker density and charge, introducing hydrophilic or steric-protecting chemical modifications (e.g., PEGylation), or using reversible side-chain chemistries to prevent kinetic trapping in solid states. Under appropriate solvent or ionic conditions, these strategies help maintain dynamic, reversible, and fluid condensates.

3.3 Dynamic Behavior and Mechanistic Insights into Peptide Condensates

The material properties of condensates, from liquid to gel to solid, are central to functional performance.⁵⁴ In peptide systems,⁵⁵ fluorescence recovery after photobleaching (FRAP) commonly reveals slower recovery and reduced mobility in droplets enriched in aromatic or hydrophobic residues, whereas more polar or weakly interacting sequences tend to display faster recovery and more liquid-like dynamics.⁵⁵ Molecular dynamics (MD) simulations complement these observations by providing atomistic or coarse-grained insight into binding energies, hydration effects, and internal mobility.⁵⁶ MD studies have shown that stronger peptide–peptide interactions slow diffusion, whereas stronger peptide–water interactions promote mobility, trends that are recapitulated across minimal peptide and coacervate models. However, simulations face practical limitations: atomistic MD is constrained in timescales and system size, limiting access to long-term maturation or multiphase organization, while coarse-grained models extend spatiotemporal range at the cost of chemical detail and sequence specificity.^{57,58} Additional challenges include parameterization and benchmarking, as inaccurate force fields can lead to overstabilized interactions or misrepresented solvent dynamics.

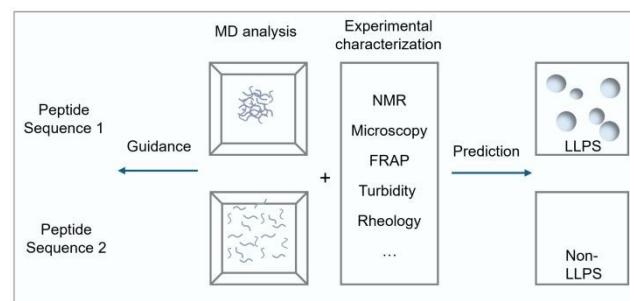


Fig. 5 Integrated simulation–experiment workflow. MD analyses (e.g., all-atom and coarse-grained simulations, association-propensity/interaction-energy calculations) together with experimental characterization (NMR, microscopy, FRAP, turbidity, rheology, etc.) jointly provide training data to predict LLPS versus non-LLPS behavior and to guide rational peptide sequence design.

In functional design, achieving phase separation is only a first step; tuning fluidity is often more critical for task-specific applications. Simulations are valuable for hypothesis generation and for mapping sequence-mobility relationships, but they are most effective when calibrated against experimental measurements such as FRAP, NMR, or rheology. In peptide condensates through LLPS, even small sequence modifications (e.g., replacing an aromatic residue with a less interactive one) can substantially alter mobility, underscoring the value of integrating simulations and experiments. To illustrate this synergy, Fig. 5 provides a schematic overview of how MD analyses and experimental data are combined to assess LLPS propensity and guide sequence design.

4. Stimuli-Responsive Properties of Peptide Condensates

Peptide condensates offer a unique opportunity to encode responsiveness into minimal molecular systems. In biology, membraneless organelle assemble, dissolve, or reorganize in response

to diverse physicochemical cues associated with stress, development, or metabolism.^{59, 60} Mimicking such dynamic regulation is a defining advantage of peptide LLPS, enabling switch-like control over assembly, internal organization, and function.^{29, 61} Here we highlight how pH, temperature, redox state, enzymatic activity, and metabolites have been used to modulate peptide LLPS, and what design principles emerge from these studies.

4.1 pH and Temperature

pH and temperature are among the most common and precisely tunable stimuli for modulating peptide LLPS. They regulate phase separation by altering the ionization state, hydrophobicity, and solvent interactions of peptide chains. Changes in pH can directly influence electrostatic interactions and the protonation states of amino acid side chains. For example, in early work by the Ali group, they demonstrated that LLPS of histidine-rich squid beak peptides (HBP-1 and its fragment GY-23) occurred in a narrow pH range of 6.0–7.5 at concentrations above 20–30 μ M. High-resolution NMR revealed that as pH gradually increased from 3.3 to 7.0, histidine residues became deprotonated, enabling the formation of transient hydrogen bonds with the phenolic hydroxyl groups of tyrosine, which stabilized the coacervate phase. At pH > 11, deprotonation of tyrosine hydroxyl groups disrupts this hydrogen-bond network, leading to gradual condensate disassembly.⁶²

Temperature provides another axis of control. Systems that are homogeneous at elevated temperature and phase-separate upon cooling display upper critical solution temperature (UCST) behavior, whereas systems that are miscible at lower temperature but separate into coexisting phases upon heating exhibit lower critical solution temperature (LCST) behavior (Fig. 6a). Depending on sequence and solvent conditions, peptide-based systems may also show closed-loop or dual UCST/LCST phase diagrams, reflecting the balance between enthalpic interactions and entropy-driven dehydration at different temperatures. Tanaka et al. investigated branched elastin-like peptide (ELP) systems based on an oligo (Glu) backbone with pendant FPGVG pentapeptides.⁶³ Upon heating, the solution became turbid around 60 °C, corresponding to dehydration and coacervation of the peptides, while further heating to 90 °C restored transparency, indicating rehydration and redissolution. The reversible temperature cycling between 20 °C, 60 °C, and 90 °C was confirmed by turbidity measurements and photographic observation. They found that increasing branching density and concentration reduced the LCST and, at low concentration (0.5 mM), induced an unusual dual LCST/UCST-like transition. These observations provide design strategies for tuning operating windows and for constructing temperature-responsive condensates that can be triggered on demand.

Collectively, these studies show that minimal peptides allow direct control over responsiveness through ionization, hydration, and thermodynamics, offering a route to engineer condensates tailored to physiological environments (e.g., lysosomal pH, fever-range temperature).

4.2 Redox Responsiveness

Redox chemistry can alter the covalent connectivity and give rise to reversible structural transitions in condensates. Zhou et al. demonstrated this using the tetrapeptide WCRY, where oxidation

induced disulfide crosslinking and transformed homogeneous droplets into core–shell architectures (Fig. 6b).^{39, 41} Reduction cleaved crosslinks and restored the original morphology, concurrently redistributing encapsulated cargo.

Building on the idea of structural switching, Sun et al. introduced an additional level of control by coupling redox sensitivity with pH responsiveness.⁶⁴ In their disulfide-conjugated HBpep system, the peptides remained as monomers below pH 6.0 but underwent LLPS at neutral pH (~6.5–7.5) to form positively charged droplets of approximately 1 μ m in diameter ($\zeta \approx +15$ mV) (Fig. 6c). In the intracellular reducing environment (1 mM GSH), the droplets disassembled rapidly, releasing up to ~90 % of encapsulated EGFP within 24 h, whereas no release occurred in the absence of GSH. This “two-stage trigger” design substantially improved delivery specificity and efficiency.

Extending beyond disulfide-based designs, Netzer et al. revealed that aromatic residue composition can influence not only the balance between electrostatic and hydrophobic forces but also the coupling of LLPS stability to electron transfer processes in oxidative environments.⁴⁶ This finding suggests that redox regulation in peptide condensates can be achieved through both covalent bond modulation and subtler adjustments to side-chain chemistry, offering a broader design space for tunable responsiveness.

Redox responsiveness shows how a single chemical motif (cysteine) can encode reversible phase transitions. Yet focusing only on disulfides narrows the design space. Expanding to alternative redox-active residues, such as methionine oxidation or catechol-based chemistry, could diversify peptide-based redox control and broaden biomedical utility.

4.3 Enzymatic Responsiveness

Compared with physicochemical stimuli, enzyme-triggered LLPS offers higher biological specificity and spatial precision. This responsiveness takes advantage of the unique expression profiles and catalytic activities of enzymes in different cellular contexts, enabling condensates to form only at designated locations.

A recent example comes from Li et al., who designed the chimeric peptide DMN-SIPL that remained dispersed in solution. Upon cleavage by Hepsin (a membrane-anchored protease overexpressed in prostate cancer cells), the original peptide released a more hydrophobic fragment undergoing LLPS directly on the cell membrane.⁶⁵ The resulting condensates anchored stably at the reaction site, continuously sequestering and inactivating Hepsin. Leveraging LLPS in this way provides unique advantages over conventional assemblies: condensates form *in situ* to avoid dilution and mislocalization, maintain dynamic molecular exchange for sustained regulation, and achieve high spatial precision through enzyme-guided activation (Fig. 6d). Building on this concept, integrating enzyme responsiveness with redox or pH sensitivity could enable multi-layered logic gating, ensuring condensates form only under specific combinations of biochemical cues, thereby targeting cell types or disease states with exceptional selectivity.

Enzyme-triggered LLPS highlights how peptides can act as “biochemical logic gates,” assembling condensates only under specific intracellular conditions. The future challenge lies in multiplexing: designing peptides responsive to more than one



enzymatic input, or coupling enzymatic cues with pH/redox triggers, to achieve programmable multi-layered logic.

View Article Online
DOI: 10.1039/D5SC07607B

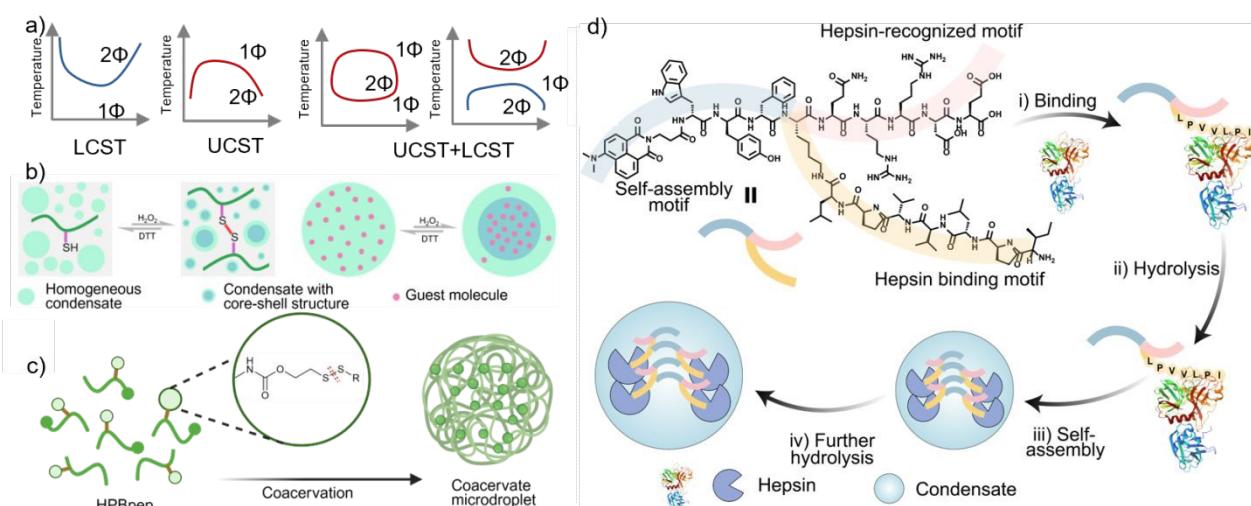


Fig. 6 Stimuli-responsive and enzymatically regulated peptide condensates. a) Schematic temperature–composition phase diagrams illustrating lower critical solution temperature (LCST), upper critical solution temperature (UCST), closed-loop (re-entrant), and dual UCST/LCST behaviors, where regions labelled “1Φ” and “2Φ” denote single-phase and two-phase regimes, respectively. b) Schematic illustration of redox-responsive condensates. External oxidative stimuli induce transformation from homogeneous droplets into core–shell structures, where encapsulated guest molecules redistribute into the newly formed core. c) Coacervation of hBpep-K peptides triggered by chemical conjugation. At neutral pH, hBpep-K remains soluble, upon attachment of a self-immolative moiety to the sole Lys residue, the peptide undergoes liquid–liquid phase separation to form microdroplets. (Created in BioRender with confirmation: BV28TBAUPM.) d) Enzymatically triggered condensates in living cells. Rationally designed amphiphilic-branched peptide DMN-SIPL assembles into solid-like condensates through LLPS upon recognition and hydrolysis by the membrane-associated serine peptidase hepsin.

4.4 Metabolite and Small-Molecule Modulation of Condensate Microenvironments

In addition to external factors such as pH, temperature, redox signals, and enzymes that regulate the phase behavior and material properties of the condensate, it is equally important that the internal microenvironment of the aggregates (including polarity and microviscosity) can also be deliberately designed. By modulating how small molecules/metabolites interact with water and peptide components, one can re-organize hydration layers and molecular mobility without changing sequence, thereby influencing multilayer miscibility, molecular partitioning, and reaction processes as an orthogonal control axis to classical stimuli.

Zhang and co-workers quantitatively mapped how various organic solutes reshape condensate microenvironments using fluorescence lifetime imaging microscopy (FLIM), FRAP, and passive microrheology. They found that microenvironmental changes do not correlate with bulk solvent polarity, instead, they track with the relative interaction strengths of solute–water versus solute–protein. Solutes with a single H-bond acceptor tend to decrease micropolarity and increase microviscosity, whereas solutes bearing multiple acceptors or forming multi-water complexes generally increase micropolarity and decrease microviscosity, enhancing molecular mobility. Notably, ATP at physiological concentrations similarly modulates condensate polarity. These microenvironmental shifts alter the miscibility of multilayer condensates and reprogram reaction rates and equilibria via changed product partitioning. Together, these data establish a measurable link from metabolites/cosolutes to hydration

organization and functional outputs, offering a practical blueprint for microenvironment engineering in peptide LLPS systems.

Metabolites should be viewed not as perturbations but as designable regulators. By embedding metabolite-binding motifs into peptides, one could create condensates that sense cellular metabolic states or act as synthetic biosensors. This aligns peptide LLPS with systems-level control in synthetic biology.

4.5 Integrative Outlook on Stimuli-Responsive Design

The examples above collectively show that peptide condensates are not passive assemblies, but programmable dynamic materials. Each type of stimulus taps into a distinct molecular principle: ionization equilibria, covalent crosslinking, proteolytic processing, or noncovalent competition. Importantly, these mechanisms are not mutually exclusive. In living systems, condensates rarely respond to a single cue, instead, they integrate multiple inputs to produce emergent behaviors such as maturation, dissolution, or functional reorganization. For peptide-based LLPS, this suggests a design map with two axes: I) Triggering mechanism (electrostatic, hydrophobic, covalent, enzymatic, metabolic). II) Functional output (assembly/disassembly, multiphase restructuring, fluid-to-solid transition, selective release). Positioning a peptide system within this map highlights both its immediate utility and potential for modular combination. For instance, a histidine-rich peptide may be extended with cysteine residues to yield dual pH–redox responsiveness, or with protease-cleavable motifs to introduce enzymatic specificity. Similarly, metabolite-binding domains could be appended to confer context-dependent regulation.

The next frontier is logic-gated condensates: droplets that form, dissolve, or reprogram only when multiple environmental conditions are satisfied. Achieving this requires layering stimuli in a rational way: for example, engineering peptides that undergo LLPS only under acidic pH and reductive conditions, or droplets that release cargo only when metabolite concentration crosses a threshold. Such “AND/OR” logic recapitulates cellular decision-making and would expand peptide LLPS beyond passive carriers into active, adaptive materials. Ultimately, stimuli-responsive peptide condensates embody the convergence of molecular design and systems-level control. By combining simple sequence motifs with programmable responsiveness, the field moves closer to building minimal synthetic organelles that not only mimic biological dynamics but also achieve functionalities not found in nature.

5 Functionalization Strategies and Emerging Applications of Peptide Condensates

As peptide-driven LLPS advances from a fundamental concept to a design platform, attention has shifted toward its functional capabilities. Peptide condensates have been engineered for biomolecule delivery, catalysis, protein stabilization, and modulation of cellular processes. Here we highlight representative examples, focusing on the design strategies that enable functionality and point toward future applications.

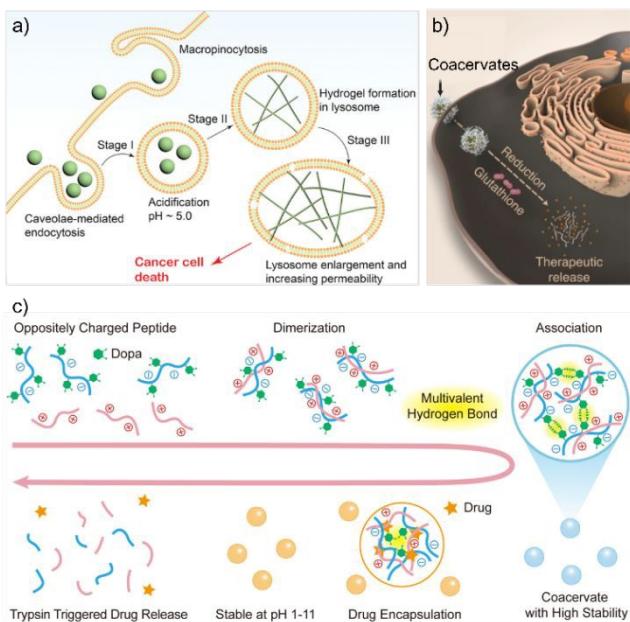


Fig. 7 Applications of peptide LLPS condensates in drug delivery. a) Phase transformation of peptide oligomers in cancer cells, with lysosomal accumulation, proton-induced hydrogel formation, and lysosomal disruption leading to cell death. b) Cytosolic delivery of therapeutics via peptide coacervates, enabled by membrane penetration and reductive disassembly. c) Oral delivery platform based on peptide coacervates, with high stability and triggered release.

5.1 Intelligent Delivery of Biomacromolecules

The environmental sensitivity of peptide LLPS allows delivery systems to release cargo only under pre-defined conditions, replacing

“blind transport” with precision targeting.⁶⁶ For example, Wang et al. designed a hexapeptide (LTP) that undergoes^{10,10^a/solution^{10,78}}

condensates transition in the acidic lysosomes of drug-resistant cancer cells. This phase transformation not only disrupted lysosomal homeostasis but also liberated chemotherapeutic agents trapped inside, thereby restoring drug sensitivity.⁶⁷ In this design, the phase transition functioned both as a delivery “switch” and as an active component of the therapeutic effect, illustrating how condensates can integrate material transformation with biological intervention (Fig. 7a).

Another strategy focuses on overcoming biological barriers to achieve direct cytosolic delivery of macromolecules. Sun et al. developed LLPS-forming peptide droplets that can penetrate cell membranes without relying on endocytosis, thereby bypassing degradative trafficking pathways.⁶⁴ Once inside, these droplets disassembled in response to the reductive intracellular environment, releasing proteins and mRNA while preserving their structural integrity and bioactivity. This work demonstrates how condensates can serve as responsive vehicles for fragile biomacromolecules that are otherwise difficult to deliver effectively (Fig. 7b).

Chen et al. further broadened the adaptability of peptide condensates by addressing oral delivery, a long-standing challenge due to gastric acidity and high-salt conditions.⁶⁸ They designed Dopa-modified peptide coacervates stabilized by multivalent hydrogen bonding, which maintained integrity in harsh gastric environments but disassembled upon recognition by intestinal enzymes. This enzyme-triggered release strategy enabled precise delivery of therapeutic proteins in the gut, highlighting how rationally engineered condensates can extend LLPS-based delivery systems to routes previously inaccessible to peptide carriers (Fig. 7c).

Collectively, these studies underscore that peptide condensates are not passive “cargo containers” but programmable delivery modules. Their responsiveness is deeply integrated into the release process, actively shaping when, where, and how therapeutic payloads are released. Such integration elevates condensates from carriers to dynamic participants in treatment, positioning peptide LLPS as a versatile platform for next-generation drug delivery. Compared with conventional polymeric nanoparticles and lipid nanoparticles (LNPs), peptide condensates operate through a distinct physical mechanism. Polymeric and lipid carriers are typically stabilized by covalent backbones or lipid bilayers, and cargo release is governed by diffusion through, or disruption of, these relatively fixed nanostructures (for example by polymer degradation, membrane fusion, or endosomal destabilization). In contrast, LLPS-derived peptide droplets are membraneless condensates formed by reversible, multivalent noncovalent interactions. Their assembly, internal viscosity, and cargo partitioning can all be tuned by environmental cues such as pH, redox state, or enzymatic activity, leading to release that is tightly coupled to condensate dissolution or reorganization. This membraneless, dynamically exchangeable nature distinguishes peptide condensates from classical nanoparticles and underpins their potential as responsive carriers for macromolecular therapeutics.

5.2 Peptide Condensates as Microreactors for Bond-Forming Reactions

Beyond delivery, peptide condensates provide confined and tuneable microenvironments that mimic cellular crowding and polarity, thereby conferring catalytic advantages. Abbas et al. engineered a disulfide-bridged dipeptide, FFssFF, which undergoes LLPS to form stable condensates in aqueous solution.³² Within these droplets, both aldol (Fig. 8a) and hydrazone (Fig. 8b) condensation reactions were markedly accelerated compared with homogeneous solution.

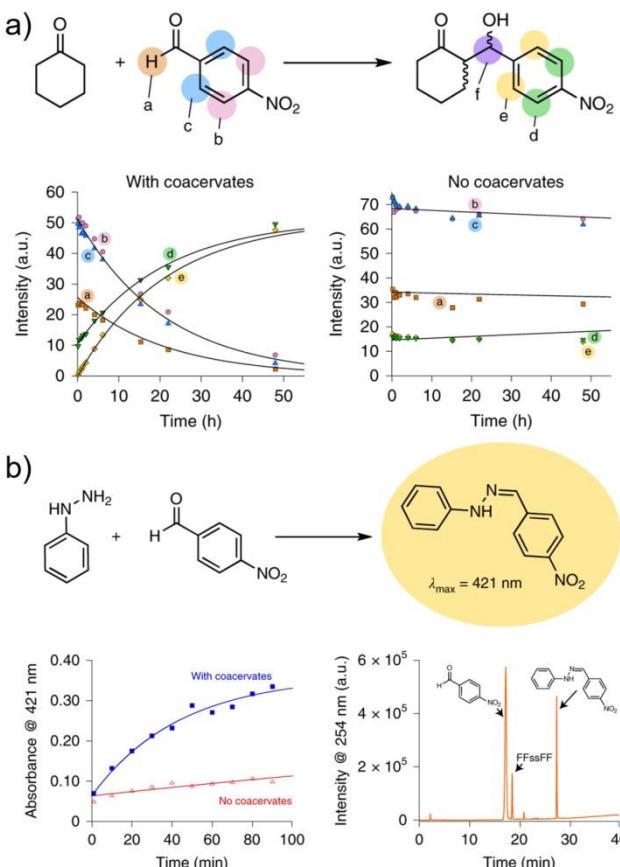


Fig. 8 Peptide condensates as catalytic microreactors. a) Aldol reaction catalyzed within FFssFF condensates, showing accelerated product formation compared with bulk solution. b) Hydrazone formation in the presence and absence of peptide condensates, highlighting enhanced reactivity within the phase-separated environment.

Specifically, aldol formation proceeded with significantly enhanced conversion, while hydrazone synthesis exhibited a ~13-fold rate increase. This catalytic effect originates from selective substrate partitioning into the condensates and from the polarity-adjusted interior, which stabilizes reactive intermediates and promotes bond formation. Such redox-responsive peptide condensates not only serve as minimal models of primitive catalytic compartments but also represent a versatile strategy to design dynamic and recyclable microreactors for chemical and biochemical transformations.

Peptide condensates represent a step toward programmable catalytic organelles. Unlike conventional nanoreactors, they offer reversibility, adaptability, and responsiveness.⁶⁹ Future directions include designing condensates that not only enhance specific reactions but also reconfigure dynamically in response to metabolic, effectively creating synthetic pathways that behave like adaptive metabolic nodes.

5.3 Preservation and Controlled Release of Biomolecules

DOI: 10.1039/D5SC07607B

The compartmentalization offered by LLPS can also extend biomolecule lifespan. Recent studies revealed that phase separation can be triggered by localized evaporation, as exemplified by Lys-Tyr-Trp (KYW) tripeptide assemblies in sessile droplets. This evaporation-driven assembly induces condensates that solidify into porous peptide microparticles, providing a robust platform for encapsulation (Fig. 9a). Dave et al. further demonstrated that such condensates can protect enzymes during drying.⁵² Upon rehydration, the particles rapidly disassemble, releasing fully active biomolecules, with nearly 100% enzymatic activity retained after 15 days of storage. This mechanism echoes natural strategies where organisms employ phase separation to preserve vital components under drought stress and suggests that synthetic peptide condensates could serve as substitutes for cold-chain storage of vaccines or enzyme therapeutics. In addition, evaporation-driven peptide condensates exhibit the capacity to recruit payload molecules through dynamic side-chain interactions, enabling versatile encapsulation and controlled release (Fig. 9b). Such properties highlight their potential as practical platforms for biomolecule preservation and stimulus-responsive delivery in biomedical applications.

Peptide LLPS offers a potential alternative to cold-chain storage, with direct implications for vaccines, enzymes, and RNA-based therapeutics.⁷⁰ The convergence of encapsulation (for preservation) and stimuli-responsive release (for delivery) suggests a continuum where condensates function as both storage reservoirs and delivery vehicles, a duality rarely seen in other material systems.

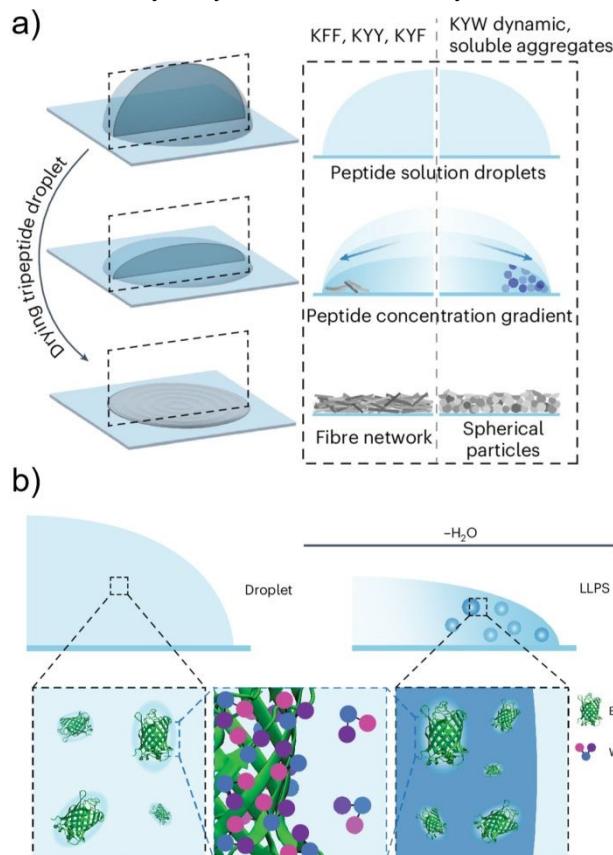


Fig. 9 Schematic illustrations of evaporation-driven peptide LLPS and its role in biomolecule encapsulation. a) Evaporation-induced self-assembly of

peptide condensates in sessile droplets. b) Payload uptake into peptide condensates via dynamic side-chain interactions and subsequent encapsulation during LLPS.

5.4 Regulation of Cell Fate and Disease Intervention

At a higher biological level, the significance of LLPS extends beyond material encapsulation to include information regulation. Kodali et al. comprehensively reviewed how condensates orchestrate transcriptional programs and cell fate in immune systems. In these contexts, condensates integrate environmental and signalling cues to modulate differentiation, activation, and effector functions.⁷¹ Although this review focused on protein-driven condensates, the conceptual framework strongly suggests that peptide condensates could be engineered to achieve similar regulatory control. As we mentioned above, Li et al. developed protease-cleavable peptides that undergo LLPS selectively in prostate cancer cells. Upon cleavage, hydrophobic fragments nucleated condensates at the plasma membrane, disrupting signaling and suppressing proliferation. This study demonstrated that peptides can be programmed as context-sensitive therapeutic effectors, with LLPS triggered only in diseased environments,⁷² which could also be used in immune system. Pathological proteins such as TDP-43 and FUS undergo LLPS-driven aggregation in neurodegeneration.^{53, 73} Synthetic peptides could intervene by co-condensing with or disrupting these assemblies, offering a new therapeutic strategy for proteinopathies. As application scenarios expand, the research focus is shifting from “whether condensates can form” to “how to ensure they function precisely at the right time, place, and under the right conditions.”

We see these strands converging toward a new paradigm of synthetic regulatory biology with peptide LLPS. Peptide condensates could one day act as programmable intracellular logic circuits, forming, dissolving, or remodelling only in response to disease-specific cues. Unlike large proteins, peptides offer tunability, responsiveness, and reduced immunogenicity, making them uniquely suited for therapeutic engineering. The immediate challenge is to bridge the minimalism of peptide motifs with the complexity of cellular networks, while success here could transform peptide LLPS into a modality for immunotherapy, cancer therapy, neurodegeneration, and regenerative medicine.

6. Future Perspectives

Peptide condensates through LLPS represent a versatile and programmable class of biomolecular assemblies. They have already shown potential in targeted delivery, catalysis, preservation, and cellular regulation. To transition from proof-of-concept systems to robust technologies, however, several obstacles remain. Below, we outline the major challenges and suggest possible strategies to address them, followed by a vision for the field’s broader promise.

6.1 Key Challenges and Possible Solutions

(1) Predictive sequence–property relationships: Currently, peptide LLPS design relies heavily on empirical screening. Subtle variations in sequence or environment can lead to very different behaviors, and unlike protein LLPS, peptide systems lack extensive databases. Establish curated peptide LLPS libraries, recording phase behavior

(critical concentration, dynamics, responsiveness, morphology).⁷⁴ These datasets can be used to train machine-learning models, enabling predictive sequence-to-property maps and rational design frameworks.

(2) Stability and control in complex environments: Condensates are inherently dynamic, which makes them responsive but also prone to premature dissolution or solidification, especially under physiological stress. Develop orthogonal multi-stimuli control strategies to ensure that droplets only form or dissolve in precisely defined contexts. Hybrid systems (peptide–polymer, peptide–RNA) may also balance stability with adaptability.

(3) Scalable synthesis and multifunctionality: Large-scale peptide synthesis is more accessible than proteins but remains costly, especially for sequences requiring chemical modifications. Integrating multiple responsive motifs into short peptides can also destabilize LLPS. Use modular building blocks where responsive motifs are introduced via minimal substitutions or post-synthetic conjugations. Advances in automated peptide synthesis and bio-orthogonal chemistries will lower cost and expand modularity.

(4) In situ formation and functional control in living systems: Most demonstrations of peptide LLPS remain *in vitro*, leaving open questions of how these condensates behave once introduced into the crowded, multicomponent environment of living cells. Key challenges include triggering phase separation *in situ* with spatial and temporal precision, maintaining condensate stability without uncontrolled maturation or dissolution, and ensuring that droplets perform defined functions rather than causing unintended cellular stress. Translation into medicine also requires understanding biodistribution, clearance, and potential immunogenicity. New strategies should focus on engineering peptides that undergo LLPS only in response to well-defined intracellular cues (e.g., protease activity, metabolite concentration, redox state), enabling spatiotemporal control of assembly. Advanced imaging and spectroscopic tools will be essential to visualize condensates in real time and to monitor their dynamic functions. Parallel efforts in pharmacokinetics and immunogenicity testing will be needed to support clinical translation.

Despite these advances, the path from laboratory prototypes to broad deployable dynamic modules still present significant challenges. Key priorities include establishing predictive sequence–function relationships, developing scalable and cost-effective synthesis methods, achieving robust and reversible control over condensate formation in complex biological environments, and integrating multifunctional modules without compromising stability. Addressing these issues will not only deepen our understanding of liquid–liquid phase separation in biological systems but also unlock the full potential of peptide condensates as programmable tools for biomedicine, synthetic biology, and molecular engineering.

6.2 Outlook

Looking forward, peptide LLPS condensates hold the potential to evolve into a true platform technology that unites chemistry, biology, and materials science. Their minimalism makes them uniquely suited to act as programmable “synthetic organelles” in synthetic biology, where spatial control over enzymatic pathways and signalling can rewire cellular behaviors. At the same time, realizing peptide-based



Perspective

synthetic organelles will require overcoming conceptual challenges such as achieving multi-input control, ensuring orthogonality to native condensates, and establishing reliable links between condensate dynamics and functional outputs.

In medicine, they may become highly specific therapeutic effectors, assembling only in diseased environments to regulate signaling or buffer pathological aggregation. In materials science, their tunable responsiveness offers routes to adaptive catalysts, sensors, and preservation systems that outperform conventional polymers. At the same time, as minimal models, peptide condensates will continue to provide fundamental insights into the molecular grammar of phase separation, deepening our understanding of protein condensates and soft matter physics.

Our perspective is that the next decade will be defined by efforts to reconcile the simplicity of peptides with the complexity of cellular systems. By integrating rational design, high-throughput experimentation, and machine learning, peptide LLPS can move from descriptive observation to predictive engineering. Ultimately, this transformation will enable peptide condensates to evolve from biomimetic curiosities into practical and transformative tools for synthetic biology, biomedicine, and materials science.

Data availability

No primary research results, software or code have been included and no new data were generated or analysed as part of this review.

Author contributions

L.L.: visualization, investigation, writing-original draft, review& editing. H. W.: supervision, resources, funding acquisition, writing-review & editing, project administration.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

This project was supported by the National Natural Science Foundation of China (U24A2076).

References

1. S. F. Banani, H. O. Lee, A. A. Hyman and M. K. Rosen, Biomolecular condensates: organizers of cellular biochemistry, *Nat Rev Mol Cell Bio*, 2017, **18**, 285-298.
2. A. A. Hyman, C. A. Weber and F. Jülicher, Liquid-Liquid Phase Separation in Biology, *Annu Rev Cell Dev Bi*, 2014, **30**, 39-58.
3. Y. Shin and C. P. Brangwynne, Liquid phase condensation in cell physiology and disease, *Science*, 2017, **357**, eaaf4382-eaaf4382.
4. B. S. Visser, W. P. Lipinski and E. Spruijt, The role of biomolecular condensates in protein aggregation, *Nat Rev Chem*, 2024, **8**, 686-700.
5. C. P. Brangwynne, C. R. Eckmann, D. S. Courson, A. Rybarska, C. Hoege, J. Gharakhani, F. Jülicher and A. A. Hyman, Germline P Granules Are Liquid Droplets That Localize by Controlled Dissolution/Condensation, *Science*, 2009, **324**, 1729-1732.
6. S. Jain, J. R. Wheeler, R. W. Walters, A. Agrawal, A. Barsic and R. Parker, ATPase-Modulated Stress Granules Contain a Diverse Proteome and Substructure, *Cell*, 2016, **164**, 487-498.
7. H. X. Zhou, D. Kota, S. B. Qin and R. Prasad, Fundamental Aspects of Phase-Separated Biomolecular Condensates, *Chem Rev*, 2024, **124**, 8550-8595.
8. A. Abyzov, M. Blackledge and M. Zweckstetter, Conformational Dynamics of Intrinsically Disordered Proteins Regulate Biomolecular Condensate Chemistry, *Chem Rev*, 2022, **122**, 6719-6748.
9. M. L. Huggins, Thermodynamic Properties of Solutions of Long - Chain Compounds, *Ann Ny Acad Sci*, 1942, **43**, 1-32.
10. Y. Ozawa, H. Anbo, M. Ota and S. Fukuchi, Classification of proteins inducing liquid-liquid phase separation: sequential, structural and functional characterization, *J Biochem*, 2022, **173**, 255-264.
11. S. V. Razin and A. A. Gavrilov, The Role of Liquid-Liquid Phase Separation in the Compartmentalization of Cell Nucleus and Spatial Genome Organization, *Biochemistry (Moscow)*, 2020, **85**, 643-650.
12. P. J. Flory, Thermodynamics of high polymer solutions, *J Chem Phys*, 1942, **10**, 51-61.
13. M. Kato, T. N. W. Han, S. H. Xie, K. Shi, X. L. Du, L. C. Wu, H. Mirzaei, E. J. Goldsmith, J. Longgood, J. M. Pei, N. V. Grishin, D. E. Frantz, J. W. Schneider, S. Chen, L. Li, M. R. Sawaya, D. Eisenberg, R. Tycko and S. L. McKnight, Cell-free Formation of RNA Granules: Low Complexity Sequence Domains Form Dynamic Fibers within Hydrogels, *Cell*, 2012, **149**, 753-767.
14. P. L. Li, S. Banjade, H. C. Cheng, S. Kim, B. Chen, L. Guo, M. Llaguno, J. V. Hollingsworth, D. S. King, S. F. Banani, P. S. Russo, Q. X. Jiang, B. T. Nixon and M. K. Rosen, Phase transitions in the assembly of multivalent signalling proteins, *Nature*, 2012, **483**, 336-340.
15. W. K. Cho, J. H. Spille, M. Hecht, C. Lee, C. Li, V. Grube and I. I. Cisse, Mediator and RNA polymerase II clusters associate in transcription-dependent condensates, *Science*, 2018, **361**, 412-415.
16. M. J. Du and Z. J. J. Chen, DNA-induced liquid phase condensation of cGAS activates innate immune signaling, *Science*, 2018, **361**, 704-709.
17. A. R. Strom, A. V. Emelyanov, M. Mir, D. V. Fyodorov, X. Darzacq and G. H. Karpen, Phase separation drives heterochromatin domain formation, *Nature*, 2017, **547**, 241-245.
18. X. L. Su, J. A. Ditlev, E. F. Hui, W. M. Xing, S. Banjade, J. Okrut, D. S. King, J. Taunton, M. K. Rosen and R. D. Vale, Phase separation of signaling molecules promotes T cell receptor signal transduction, *Science*, 2016, **352**, 595-599.
19. M. L. Zeng, Y. Shang, Y. Araki, T. F. Guo, R. L. Huganir and M. J. Zhang, Phase Transition in Postsynaptic Densities Underlies Formation of Synaptic Complexes and Synaptic Plasticity, *Cell*, 2016, **166**, 1163-1175.
20. G. M. Zhang, Z. Wang, Z. Du and H. Zhang, mTOR Regulates Phase Separation of PGL Granules to Modulate Their Autophagic Degradation, *Cell*, 2018, **174**, 1492-1506.

Chemical Science



Perspective

Chemical Science

21. A. Molliex, J. Temirov, J. Lee, M. Coughlin, A. P. Kanagaraj, H. J. Kim, T. Mittag and J. P. Taylor, Phase Separation by Low Complexity Domains Promotes Stress Granule Assembly and Drives Pathological Fibrillization, *Cell*, 2015, **163**, 123-133.

22. B. Wang, L. Zhang, T. Dai, Z. R. Qin, H. S. Lu, L. Zhang and F. F. Zhou, Liquid-liquid phase separation in human health and diseases, *Signal Transduct Tar*, 2021, **6**: 290.

23. X. Yan, D. Kuster, P. Mohanty, J. Nijssen, K. Pombo-García, J. G. Morato, A. Rizuan, T. M. Franzmann, A. Sergeeva, A. M. Ly, F. L. Liu, P. M. Passos, L. George, S. H. Wang, J. Shenoy, H. L. Danielson, B. Ozguney, A. Honigmann, Y. M. Ayala, N. L. Fawzi, D. W. Dickson, W. Rossoll, J. Mittal, S. Alberti and A. A. Hyman, Intra-condensate demixing of TDP-43 inside stress granules generates pathological aggregates, *Cell*, 2025, **188**, 4123-4140.

24. E. W. Martin, A. S. Holehouse, I. Peran, M. Farag, J. J. Incicco, A. Bremer, C. R. Grace, A. Soranno, R. V. Pappu and T. Mittag, Valence and patterning of aromatic residues determine the phase behavior of prion-like domains, *Science*, 2020, **367**, 694-699.

25. S. Rekhi, C. G. Garcia, M. Barai, A. Rizuan, B. S. Schuster, K. L. Kiick and J. Mittal, Expanding the molecular language of protein liquid-liquid phase separation, *Nat Chem*, 2024, **16**, 1113-1124.

26. R. van der Lee, M. Buljan, B. Lang, R. J. Weatheritt, G. W. Daughdrill, A. K. Dunker, M. Fuxreiter, J. Gough, J. Gsponer, D. T. Jones, P. M. Kim, R. W. Kriwacki, C. J. Oldfield, R. V. Pappu, P. Tompa, V. N. Uversky, P. E. Wright and M. M. Babu, Classification of Intrinsically Disordered Regions and Proteins, *Chem Rev*, 2014, **114**, 6589-6631.

27. M. Abbas, W. P. Lipin, J. Wang and E. Spruijt, Peptide-based coacervates as biomimetic protocells, *Chem Soc Rev*, 2021, **50**, 3690-3705.

28. R. Kubota, S. Torigoe and I. Hamachi, Temporal Stimulus Patterns Drive Differentiation of a Synthetic Dipeptide-Based Coacervate, *J Am Chem Soc*, 2022, **144**, 15155-15164.

29. G. L. Li, C. Q. Yuan and X. H. Yan, Peptide-mediated liquid-liquid phase separation and biomolecular condensates, *Soft Matter*, 2025, **21**, 1781-1812.

30. J. M. Choi and R. V. Pappu, The Stickers and Spacers Framework for Describing Phase Behavior of Multivalent Intrinsically Disordered Proteins, *Biophys J*, 2020, **118**, 492a-492a.

31. S. Ranganathan and E. I. Shakhnovich, Dynamic metastable long-living droplets formed by sticker-spacer proteins, *Elife*, 2020, **9**: e56159.

32. M. Abbas, W. P. Lipiński, K. K. Nakashima, W. T. S. Huck and E. Spruijt, A short peptide synthon for liquid-liquid phase separation, *Nat Chem*, 2021, **13**, 1046-1054.

33. V. Castelletto, J. Seitsonen, A. Pollitt and I. W. Hamley, Minimal Peptide Sequences That Undergo Liquid-Liquid Phase Separation via Self-Coacervation or Complex Coacervation with ATP, *Biomacromolecules*, 2024, **25**, 5321-5331.

34. Y. Dai, L. You and A. Chilkoti, Engineering synthetic biomolecular condensates, *Nat. Rev. Bioeng*, 2023, **1**, 466-480.

35. J. M. Choi, A. S. Holehouse and R. V. Pappu, Physical Principles Underlying the Complex Biology of Intracellular Phase Transitions, *Annu Rev Biophys*, 2020, **49**, 107-133.

36. S. L. Perry, L. Leon, K. Q. Hoffmann, M. J. Kade, D. Priftis, K. A. Black, D. Wong, R. A. Klein, C. F. Pierce, K. Margossian, J. K. Whitmer, J. Qin, J. J. de Pablo and M. Tirrell, Chirality-selected phase behaviour in ionic polypeptide complexes, *Nat Commun*, 2015, **6**: 6052.

37. F. P. Cakmak, S. Choi, M. O. Meyer, P. C. Bevilacqua and C. D. Keating, Prebiotically-relevant low polyion multivalency can improve functionality of membraneless compartments, *Nat Commun*, 2020, **11**:5949.

38. B. Gabryelczyk, H. Cai, X. Y. Shi, Y. Sun, P. J. M. Swinkels, S. Salentinig, K. Pervushin and A. Miserez, Hydrogen bond guidance and aromatic stacking drive liquid-liquid phase separation of intrinsically disordered histidine-rich peptides, *Nat Commun*, 2019, **10**: 5465.

39. L. Zhou, L. Zhu, C. Wang, T. Xu, J. Wang, B. Zhang, X. Zhang and H. Wang, Multiphasic condensates formed with mono-component of tetrapeptides via phase separation, *Nat Commun*, 2025, **16**: 2706.

40. K. Kaygisiz, D. Sementa, V. Athiyarath, X. Chen and R. V. Ulijn, Context dependence in assembly code for supramolecular peptide materials and systems, *Nat Rev Mater*, 2025, **10**, 449-472.

41. H. R. Kilgore and R. A. Young, Learning the chemical grammar of biomolecular condensates, *Nat Chem Biol*, 2022, **18**, 1298-1306.

42. W. M. Aumiller and C. D. Keating, Phosphorylation-mediated RNA/peptide complex coacervation as a model for intracellular liquid organelles, *Nat Chem*, 2016, **8**, 129-137.

43. B. Saha, A. Chatterjee, A. Reja and D. Das, Condensates of short peptides and ATP for the temporal regulation of cytochrome activity, *Chem Commun*, 2019, **55**, 14194-14197.

44. D. L. J. Lafontaine, J. A. Riback, R. Bascetin and C. P. Brangwynne, The nucleolus as a multiphase liquid condensate, *Nat Rev Mol Cell Bio*, 2021, **22**, 165-182.

45. L. C. Zhou, L. H. Lu, Y. Zhang, J. Wang, J. J. Cheng and H. M. Wang, Water Dynamics in the Formation of Single-Component-Based Multiphasic Droplets, *J Am Chem Soc*, 2025, **147**, 31290-31299.

46. A. Netzer, A. Baruch Leshem, S. Veretnik, I. Edelstein and A. Lampel, Regulation of Peptide Liquid-Liquid Phase Separation by Aromatic Amino Acid Composition, *Small*, 2024, **20**, 2401665.

47. S. Ye, A. P. Latham, Y. Tang, C.-H. Hsiung, J. Chen, F. Luo, Y. Liu, B. Zhang and X. Zhang, Micropolarity governs the structural organization of biomolecular condensates, *Nat Chem Biol*, 2024, **20**, 443-451.

48. S. S. Ribeiro, N. Samanta, S. Ebbinghaus and J. C. Marco, The synergic effect of water and biomolecules in intracellular phase separation, *Nat Rev Chem*, 2019, **3**, 552-561.

49. S. Arya, A. K. Sinh, T. Khan, M. Bhattacharya, A. Datta and S. Mukhopadhyay, Water Rearrangements upon Disorder-to-Order Amyloid Transition, *J Phys Chem Lett*, 2016, **7**, 4105-4110.

50. D. Thirumalai, G. Reddy and J. E. Straub, Role of Water in Protein Aggregation and Amyloid Polymorphism, *Accounts Chem Res*, 2012, **45**, 83-92.

51. C. Yuan, R. Xing, J. Cui, W. Fan, J. Li and X. Yan, Multistep Desolvation as a Fundamental Principle Governing Peptide



Perspective

Chemical Science

Self-Assembly Through Liquid–Liquid Phase Separation, *CCS Chem*, 2023, **6**, 255–265.

52. D. R. Dave, S. Kassem, M. Coste, L. Xu, M. Tayarani-Najjaran, D. Podbevsek, P. Colon-De Leon, S. Zhang, L. Ortuno Macias, D. Sementa, M. Pérez-Ferreiro, N. S. Ayati, M. A. Choudhury, K. Veerasammy, S. Doganata, T. Zhong, C. Weng, J. Morales, D. C. Favaro, M. Marianski, S. Y. Ahn, A. C. Obermeyer, T. Wang, T.-D. Li, X. Chen, R. Tu, Y. He and R. V. Ulijn, Adaptive peptide dispersions enable drying-induced biomolecule encapsulation, *Nat. Mater.*, 2025, **24**, 1465–1475.

53. H. Gong, Y. Sakaguchi, T. Suzuki, M. Yanagisawa and T. Aida, Near-identical macromolecules spontaneously partition into concentric circles, *Nature*, 2024, **636**, 92–99.

54. S. Jiao, D. M. R. Mirabal, A. J. DeStefano, R. A. Segalman, S. Han and M. S. Shell, Sequence Modulates Polypeptoid Hydration Water Structure and Dynamics, *Biomacromolecules*, 2022, **23**, 1745–1756.

55. L. Jawerth, E. Fischer-Friedrich, S. Saha, J. Wang, T. Franzmann, X. J. Zhang, J. Sachweh, M. Ruer, M. Ijavi, S. Saha, J. Mahamid, A. A. Hyman and F. Jülicher, Protein condensates as aging Maxwell fluids, *Science*, 2020, **370**, 1317–1323.

56. M. T. Ivanović and R. B. Best, All-atom simulations of biomolecular condensates, *Curr. Opin. Struct. Biol.*, 2025, **93**, 103101.

57. L. X. Cao, B. Coventry, I. Goreshnik, B. W. Huang, W. Sheffler, J. S. Park, K. M. Jude, I. Markovic, R. U. Kadam, K. H. G. Verschueren, K. Verstraete, S. T. R. Walsh, N. Bennett, A. Phal, A. Yang, L. Kozodoy, M. DeWitt, L. Picton, L. Miller, E. M. Strauch, N. D. DeBouver, A. Pires, A. K. Bera, S. Halabiya, B. Hammerson, W. Yang, S. Bernard, L. Stewart, I. A. Wilson, H. Ruohola-Baker, J. Schlessinger, S. Lee, S. N. Savvides, K. C. Garcia and D. Baker, Design of protein-binding proteins from the target structure alone, *Nature*, 2022, **605**, 551–560.

58. D. E. Shaw, P. Maragakis, K. Lindorff-Larsen, S. Piana, R. O. Dror, M. P. Eastwood, J. A. Bank, J. M. Jumper, J. K. Salmon, Y. B. Shan and W. Wriggers, Atomic-Level Characterization of the Structural Dynamics of Proteins, *Science*, 2010, **330**, 341–346.

59. S. Alberti, A. Gladfelter and T. Mittag, Considerations and Challenges in Studying Liquid–Liquid Phase Separation and Biomolecular Condensates, *Cell*, 2019, **176**, 419–434.

60. S. Chagri, D. Y. W. Ng and T. Weil, Designing bioresponsive nanomaterials for intracellular self-assembly, *Nat Rev Chem*, 2022, **6**, 320–338.

61. Y. Bao, H. Chen, Z. Xu, J. Gao, L. Jiang and J. Xia, Photo - Responsive Phase - Separating Fluorescent Molecules for Intracellular Protein Delivery, *Angew. Chem. Int. Ed.*, 2023, **62**, e202307045.

62. B. Gabryelczyk, H. Cai, X. Shi, Y. Sun, P. J. M. Swinkels, S. Salentinig, K. Pervushin and A. Miserez, Hydrogen bond guidance and aromatic stacking drive liquid–liquid phase separation of intrinsically disordered histidine-rich peptides, *Nat Commun*, 2019, **10**: 5465.

63. N. Tanaka, K. Suyama, K. Tomohara and T. Nose, Exploring LCST- and UCST-like Behavior of Branched Molecules Bearing Repeat Units of Elastin-like Peptides as Side Components, *Biomacromolecules*, 2024, **25**, 7156–7166.

64. Y. Sun, S. Y. Lau, Z. W. Lim, S. C. Chang, F. Ghadessy, A. Partridge and A. Miserez, Phase-separating peptides for direct cytosolic delivery and redox-activated release of macromolecular therapeutics, *Nat Chem*, 2022, **14**, 274–283.

65. Y. Li, T. Xu, Y. Li and H. Wang, Enzyme Induced Solid-Like Condensates Formation of Engineered Peptide in Living Cells for Prostate Cancer Inhibition, *Angew. Chem. Int. Ed.*, 2025, **64**, e202504958.

66. J. H. Liu, E. Spruijt, A. Miserez and R. Langer, Peptide-based liquid droplets as emerging delivery vehicles, *Nat Rev Mater*, 2023, **8**, 139–141.

67. J. Wang, L. Hu, H. Zhang, Y. Fang, T. Wang and H. Wang, Intracellular Condensates of Oligopeptide for Targeting Lysosome and Addressing Multiple Drug Resistance of Cancer, *Adv Mater*, 2021, **34**, 2104704.

68. S. Chen, G. Zou, Q. Guo, X. Qian, H. Li, H. Gao and J. Yu, Extreme pH Tolerance in Peptide Coacervates Mediated by Multivalent Hydrogen Bonds for Enzyme-Triggered Oral Drug Delivery, *J Am Chem Soc*, 2025, **147**, 9704–9715.

69. Y. L. M. Ji, Y. Y. Lin and Y. Qiao, Interfacial assembly of biomimetic MOF-based porous membranes on coacervates to build complex protocells and prototissues, *Nat. Chem*, 2025, **17**, 986–996.

70. C. Roden and A. S. Gladfelter, RNA contributions to the form and function of biomolecular condensates, *Nat Rev Mol Cell Bio*, 2021, **22**, 183–195.

71. S. Kodali, C. M. Sands, L. Guo, Y. Huang and B. Di Stefano, Biomolecular condensates in immune cell fate, *Nat. Rev. Immunol*, 2025, **25**, 445–459.

72. T. Ikenoue, M. So, N. Terasaka, W.-E. Huang, Y. Kawata, Y. Miyanoiri, K. Kamagata and H. Suga, De Novo Peptides That Induce the Liquid–Liquid Phase Separation of α -Synuclein, *J Am Chem Soc*, 2025, **147**, 24113–24126.

73. H. R. Li, W. C. Chiang, P. C. Chou, W. J. Wang and J. R. Huang, TAR DNA-binding protein 43 (TDP-43) liquid–liquid phase separation is mediated by just a few aromatic residues, *J Biol Chem*, 2018, **293**, 6090–6098.



Data availability

No primary research results, software or code have been included and no new data were generated or analysed as part of this review.